

MicroED Structure of Au₁₄₆(p-MBA)₅₇ at Subatomic Resolution Reveals a Twinned FCC Cluster

Sandra Vergara,^{†,○} Dylan A. Lukes,^{‡,○} Michael W. Martynowycz,^{§,○} Ulises Santiago,[†] Germán Plascencia-Villa,[†] Simon C. Weiss,[‡] M. Jason de la Cruz,^{§,▽} David M. Black,^{†,Ⓜ} Marcos M. Alvarez,[†] Xochitl López-Lozano,[†] Christopher O. Barnes,^{‡,#} Guowu Lin,[‡] Hans-Christian Weissker,^{||} Robert L. Whetten,^{*,†} Tamir Gonen,^{*,§,⊥,Ⓧ} Miguel Jose Yacaman,^{*,†} and Guillermo Calero^{*,‡,Ⓜ}

[†]Department of Physics and Astronomy, The University of Texas at San Antonio, San Antonio, Texas 78249, United States

[‡]Department of Structural Biology, University of Pittsburgh, Pittsburgh, Pennsylvania 15260, United States

[§]Janelia Research Campus, Howard Hughes Medical Institute, Ashburn, Virginia 20147, United States


^{||}Aix Marseille Université, CNRS, CINaM UMR 7325, Marseille 13288, France

[⊥]Howard Hughes Medical Institute, University of California, Los Angeles, Los Angeles, California 90095, United States

[Ⓧ]Departments of Physiology and Biological Chemistry, David Geffen School of Medicine, University of California, Los Angeles, Los Angeles, California 90095, United States

Supporting Information

ABSTRACT: Solving the atomic structure of metallic clusters is fundamental to understanding their optical, electronic, and chemical properties. Herein we present the structure of the largest aqueous gold cluster, Au₁₄₆(p-MBA)₅₇ (p-MBA: *para*-mercaptobenzoic acid), solved by electron micro-diffraction (MicroED) to subatomic resolution (0.85 Å) and by X-ray diffraction at atomic resolution (1.3 Å). The 146 gold atoms may be decomposed into two constituent sets consisting of 119 core and 27 peripheral atoms. The core atoms are organized in a twinned FCC structure, whereas the surface gold atoms follow a C₂ rotational symmetry about an axis bisecting the twinning plane. The protective layer of 57 p-MBAs fully encloses the cluster and comprises bridging, monomeric, and dimeric staple motifs. Au₁₄₆(p-MBA)₅₇ is the largest cluster observed exhibiting a bulk-like FCC structure as well as the smallest gold particle exhibiting a stacking fault.

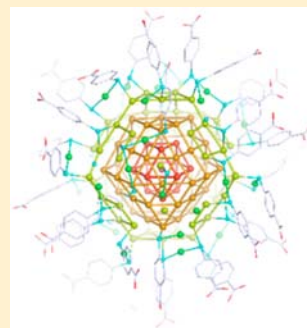

Within the field of nanotechnology, metal clusters and nanoparticles are of central interest for their optical, electronic, and chemical properties. However, advances in this field have been limited by a lack of fidelity in the growth of nanoparticles. One strategy to achieve precise control over the shape and size of nanoparticles is the use of ligands as surface-protecting agents. This approach has enabled the synthesis of numerous stable clusters with atomically well-defined composition. Spectroscopic studies reveal that smaller metallic clusters have molecule-like electronic structures, whereas larger ones support collective plasmon excitation similar to bulk-like nanoparticles.^{1–3} Solving the atomic structure of protected metal clusters is fundamental to understanding their size-dependent properties. Single crystal X-ray diffraction (XRD) has previously revealed the structure of several thiolate-protected gold clusters.^{3–14} Although some small clusters display FCC-like kernels,^{3–5} for several clusters, including the larger ones with {102, 130, 133, and 246} Au atoms, noncrystalline icosahedra and truncated decahedra (known as multiply twinned particles, or MTPs) have been found.^{11–14} However, for sufficiently large clusters, a transition to bulk-like

FCC packing should occur. Although some studies suggest a geometric and electronic transition occurring in the range of Au₁₄₄ to Au₃₂₉, the critical size for this transition is not clear.^{1,2,15–17} Therefore, the case of ubiquitous clusters of ~29 kDa core mass (1.7 nm core diameter), commonly identified as Au₁₄₄(SR)₆₀, is of particular interest. After two decades since this class of compounds was first reported,¹⁸ the precise composition and structure of the ~29 kDa cluster remains elusive. The current models predict that Au₁₄₄(SR)₆₀ should have icosahedral symmetry,^{19,20} whereas aqueous-phase samples may present polymorphism with competing icosahedral and truncated decahedral cores.²¹ However, efforts to reveal its structure have thus far been unproductive. Herein we present a novel gold cluster in the ~29 kDa size regime, Au₁₄₆(SR)₅₇, whose twinned-FCC structure departs from previous icosahedral and decahedral models proposed for Au₁₄₄(SR)₆₀.

Received: October 3, 2017

Accepted: October 26, 2017

Published: October 26, 2017

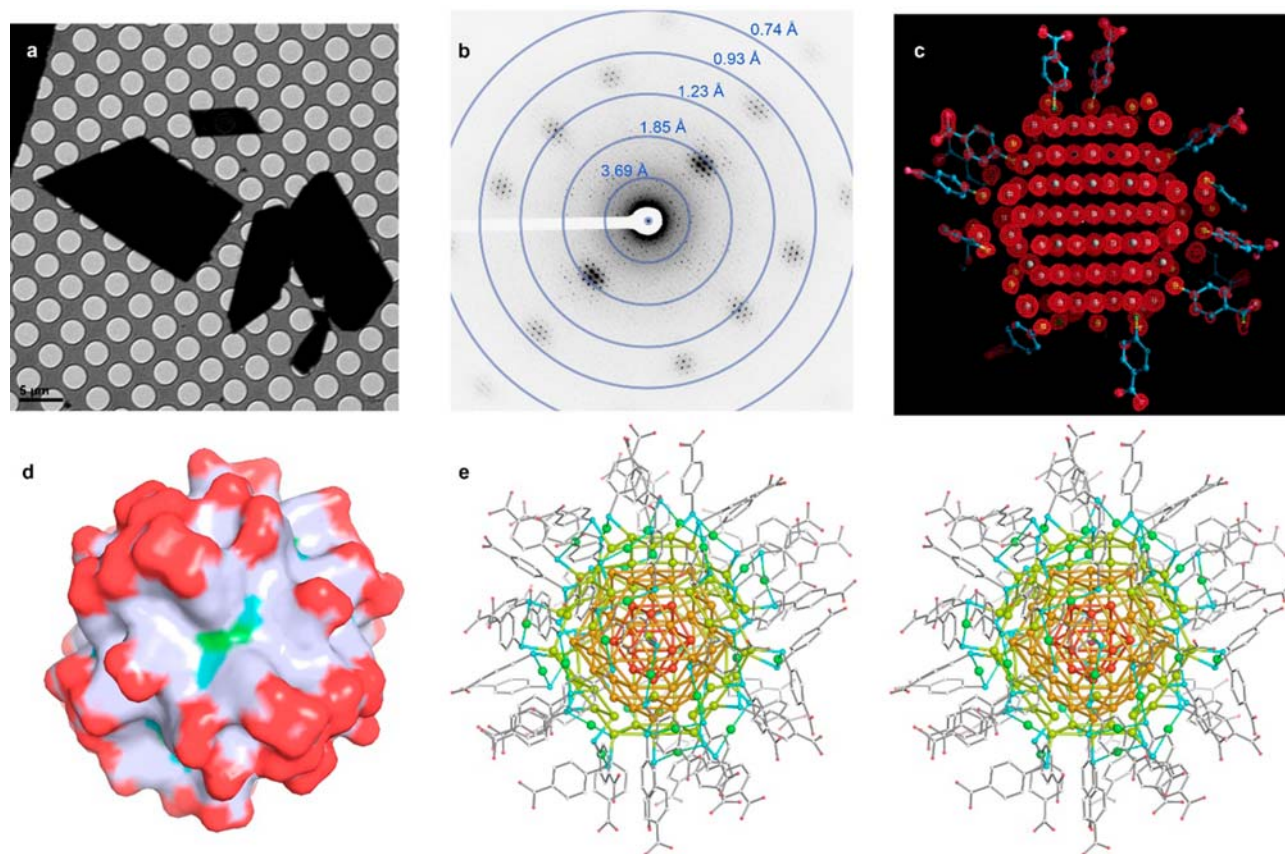


Figure 1. MicroED and X-ray determination of the crystal structure of $\text{Au}_{146}(\text{p-MBA})_{57}$. (a) Transmission electron micrograph of $\text{Au}_{146}(\text{p-MBA})_{57}$ crystals and (b) typical MicroED data extending well beyond 1 Å. (c) MicroED density map (2Fo-Fc, contoured at 2σ), shown as red mesh, identifies atomic positions of Au (white spheres) and S (yellow spheres) atoms. Ligands (p-MBA) are shown as blue framework. (d) Surface representation of the cluster with oxygen in red, carbon in white, sulfur in cyan, and gold in green. The full set of p-MBA ligands was determined using X-ray data. (e) Stereoscopic representation of the cluster including all gold atoms and p-MBA ligands. Gold atoms colored by shells for visualization purposes (see Figure 2).

Synthesis of the gold nanoclusters was achieved by a modified two-phase method,²² where clusters were precipitated by incubation in cold methanol or in cold methanol with 100 mM ammonium acetate. The product was separated by native-PAGE (Figure S1). In both cases, analysis via liquid chromatography/high-resolution electrospray ionization mass spectroscopy (HPLC/ESI-MS) methods is consistent with the $\text{Au}_{146}(\text{p-MBA})_{57}$ molecular formula (Figure S2). Thus $\text{Au}_{146}(\text{p-MBA})_{57}$ does not constitute an artifact of crystallization because it existed in solution prior to crystallization. Samples without ammonium acetate formed poorly diffracting hexagonal plate crystals similar to those previously reported,^{21,23,24} whereas samples coprecipitated with ammonium acetate crystallized as needles and plates in the presence of 25% polyethylene glycol 8000 and 50 mM sodium potassium phosphate (Table S1). Large crystals as well as fragmented nanocrystals (Figure 1a) were selected for X-ray and free electron laser (FEL), or MicroED experiments,^{25,26} respectively. X-ray analysis provided resolution of 1.3 Å, whereas hardware limitations restricted FEL data to 1.7 Å only. Remarkably, subatomic resolution was only achieved with MicroED where crystals were analyzed in a frozen hydrated state by electron diffraction (Figure 1b and Figure S3). A total of 146 gold atoms and 57 p-MBA ligands were identified in the electron density maps correlating with ESI-MS (Figure 1c). The surface representation of the metal

cluster shows a globular and well-ordered structure that is effectively coated with p-MBA, preventing further growth (Figure 1d and Movie S1). The overall architecture of the cluster is illustrated stereographically by Figure 1e. The root-mean-square deviation between MicroED and X-ray atomic positions was 0.05 Å for the cluster kernel (innermost 13 Au atoms) and 0.1 Å for the entire gold structure, confirming the equivalence of the two methods. This MicroED structure represents the highest resolution structure for such aqueous phase gold clusters and the highest resolution reported to date by any cryoEM method.

The 146 gold atoms in the $\text{Au}_{146}(\text{p-MBA})_{57}$ may be decomposed into two constituent sets: 119 core atoms and 27 peripheral atoms. The core atoms are organized in a twinned FCC structure (Figure 2a), whereas the surface gold atoms follow a C_2 rotational symmetry about an axis bisecting the twinning plane (Figure 2b). While FCC structures may be described morphologically as nested cuboctahedra, twinned FCC structures may be described as nested *anti*-cuboctahedra (Figure S4). Anticuboctahedra are also known as J27 under the Johnson solid classification system. The eight triangular faces of a J27 correspond to $\{111\}$ planes, and the six square faces correspond to $\{100\}$ planes. The core of $\text{Au}_{146}(\text{p-MBA})_{57}$ is composed of three nested J27 shells: a first shell (J27-1) formed by the 12 immediate neighbors of the central Au-atom site, a

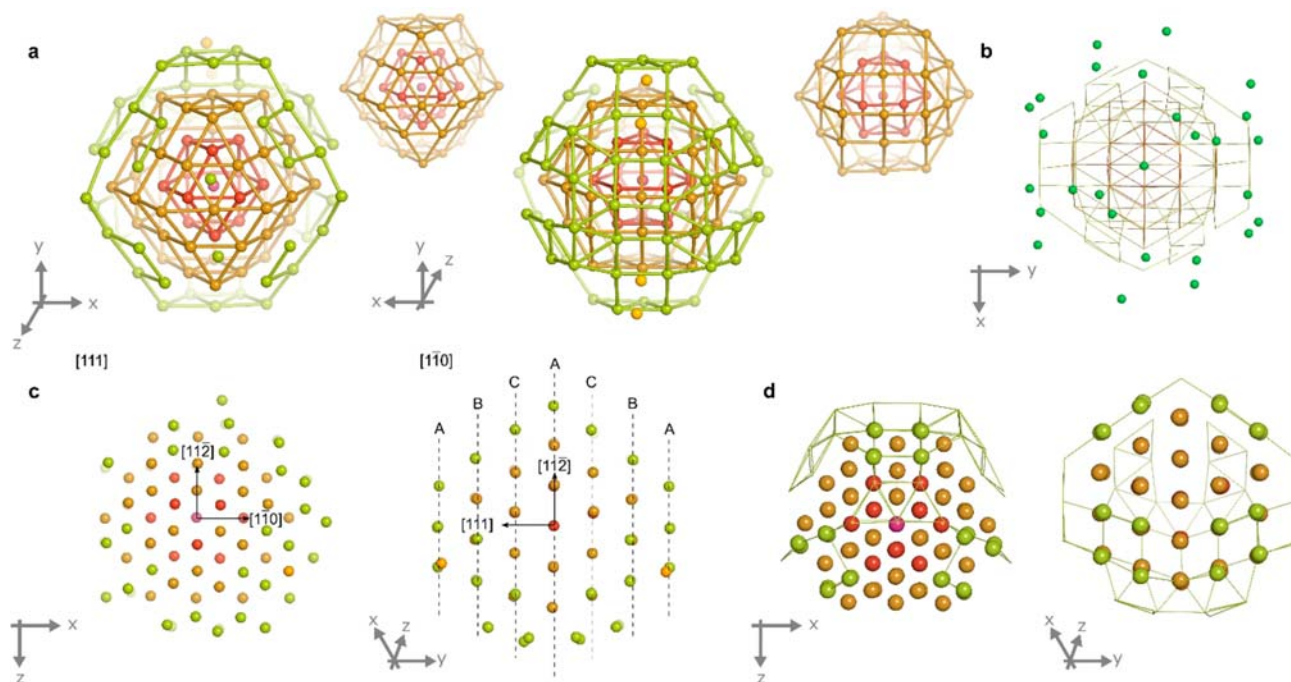


Figure 2. Configuration of gold atoms in $\text{Au}_{146}(\text{p-MBA})_{57}$. (a) Core structure (119-atoms) of the Au_{146} cluster. The central atom (purple) and the first shell J27-1 (red) comprise the kernel of the cluster, second shell J27-2 (brown), third shell J27-3 (light green), and extra atoms in the core (dark yellow). Twin plane parallel to xz -plane. (b) Location of peripheral gold atoms (27-atoms) in dark green, with core displayed in wires. (c) View of crystallographic planes. Plane directions are absolute to an FCC unit cell. (d) Selection of 79-atom corresponding to a twinned truncated octahedron, t-TO+. Remaining atoms from core displayed on wires.

second shell (J27-2) of 42 sites, and an incomplete third shell (J27-3) comprising 60 sites (115 in total). Two pairs of additional gold atoms located on $\{100\}$ facets complete the 119-atom core. The observed truncation of 32 sites, with respect to an ideal J27-3 shell, rounds the morphology (Figure S5a,b), as these truncations occur at sites of low coordination number: 12 at vertices and 20 along edges (Figure S5c–h). In particular, sites on the boundary between mirror $\{111\}$ planes are not occupied. In addition, in four of the $\{111\}$ facets, we observe a lattice distortion that resembles the HCP packing. The occupied positions as well as the distorted positions in the third shell are symmetric across mirror planes. However, nonmirror $\{111\}$ planes are distinct throughout the third shell. The view along the $[111]$ direction (Figure 2c) shows that atoms belonging to J27-1 and J27-2 as well as the majority of atoms in J27-3 lie on the expected positions for an FCC, whereas most of the peripheral atoms deviate from ideal positions (Figure 2b and Figure S6). The view along the $[1-10]$ direction shows the twin in the Au_{146} structure.

Alternatively, one notes the presence of a 79-site twinned truncated octahedron (t-TO+) as a substructure of Au_{146} (Figure 2d). The superior stability of the Marks decahedron and t-TO+ was previously predicted for gold clusters as compared with the icosahedron or the untwinned TO+.^{17,27} The 79-atom t-TO+ substructure may be recovered by capping each of the six $\{100\}$ facets of J27-2 with four gold atoms. This t-TO+ also appears as a distinguishable group in the radial distance histogram from the central atom (Figure S7).

The protective layer of $\text{Au}_{146}(\text{p-MBA})_{57}$ comprises 7 bridging motifs ($-\text{S}-$), 19 monomeric staple motifs ($-\text{S}-\text{Au}-\text{S}-$), and 4 dimeric staple motifs ($-\text{S}-\text{Au}-\text{S}-\text{Au}-\text{S}-$) arranged around the C_2 symmetry axis bisecting the twinning plane (Figure

3a,b). Four of the bridging motifs lie on $\{100\}$ facets, two connect mirror $\{111\}$ facets, and one is located on the screw axis. This bridging motif has been observed primarily on $\{100\}$ facets^{7,10} but has recently been identified linking $\{111\}$ facets in the structure of $\text{Au}_{246}(\text{p-MBT})_{80}$ ¹⁴ (Figure S8). The monomeric staples connect adjacent facets. The four dimeric staples are anchored to $\{111\}$ facets, two of them directly linked to atoms in the J27-2. Dimeric staples have been observed forming a “V” shape with the sulfur atoms in almost coplanar positions.^{9,11} In $\text{Au}_{146}(\text{p-MBA})_{57}$, the three sulfur atoms ($-\text{S}-\text{Au}-\text{S}-\text{Au}-\text{S}-$) are not coplanar, resulting in a bending of the staple. Interestingly, both characteristics of dimeric staples, the exclusive binding on $\{111\}$ facets and the bending, are also present in the nonaqueous system $\text{Au}_{246}(\text{p-MBT})_{80}$ ¹⁴ (Figure S8). The overall distribution of the staples is presented in Figure 3c.

Starting from the experimental coordinates, we have analyzed the structure by density functional theory (DFT) methods. The optimized (relaxed) structure thus obtained retains all connectivity of the original while removing many of its irregularities in interatomic distances, thereby enhancing the C_2 -symmetry feature (Figure S9). In particular, Au–S bond lengths show a bimodal distribution, in agreement with experiment, where this double-peak structure is rather broad. The first peak is at 2.297 Å and corresponds to peripheral Au–S bonds, whereas the second is at 2.360 Å and corresponds to core Au–S bonds. We also observe a strong correlation between peaks of the radial distribution function and those of an FCC structure, with a peak gold–gold distance of 2.88 Å and most atoms in the range 2.73 to 3.1 Å.

Gold clusters may manifest both crystalline FCC and noncrystalline structures. FCC cores have been observed in

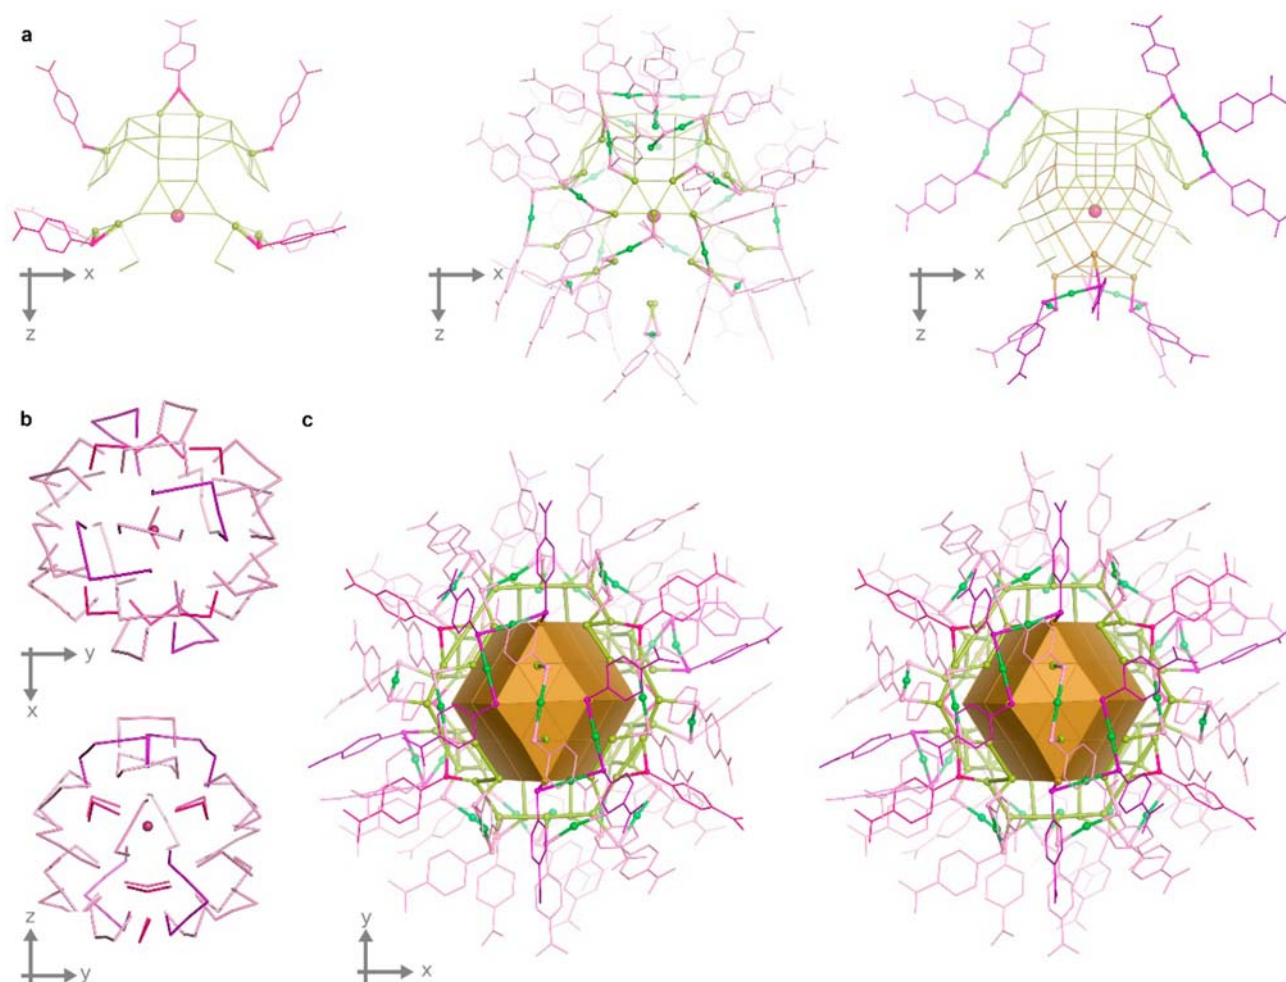


Figure 3. Configuration of ligands (p-MBA) on $\text{Au}_{146}(\text{p-MBA})_{57}$. (a) Distribution of the three types of staples on the core surface of $\text{Au}_{146}(\text{p-MBA})_{57}$. Bridging motifs (left) in pink, monomeric staples (center) in light pink, and dimeric staples (right) in purple. (b) Rotational symmetric distribution of staples. Screw axis parallel to z -axis bisecting the twin plane (xz -plane). (c) Stereoscopic view of $\text{Au}_{146}(\text{p-MBA})_{57}$ displaying all different types of staples; J27-2 atoms are displayed as solid surface.

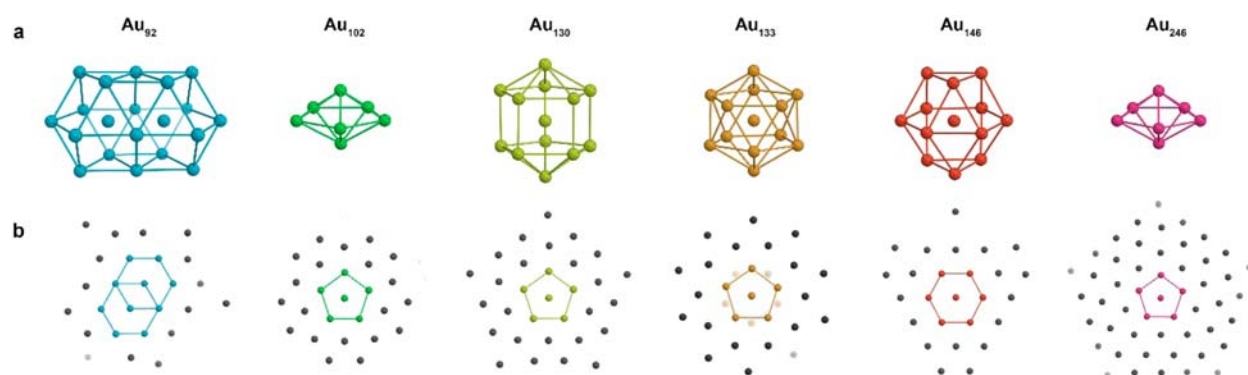


Figure 4. Atomic structures of the largest gold clusters solved to date. (a) Kernel structures of Au_{92} (conjoined cuboctahedra with no unique central atom), Au_{102} and Au_{246} (decahedra), Au_{130} (Ino decahedron), Au_{133} (icosahedron), and Au_{146} (anticuboctahedron). (b) View along the $[111]$ axis for Au_{92} and Au_{146} shows the atomic positions following the close-packing of FCC structures, whereas the projection along $[110]$ axis for Au_{102} , Au_{130} , Au_{133} , and Au_{246} shows five-fold symmetry.

some small clusters^{3–6,8} and, more recently, in the tetragonal-shaped Au_{92} .¹⁰ Other clusters, including the larger ones (Au_{102} , Au_{130} , Au_{133} , and Au_{246}), display cores with five-fold symmetry (MTPs).^{7,9,11–14} Figure 4 shows the six largest gold clusters

solved to date. Au_{92} ¹⁰ presents an FCC core; Au_{102} ,¹¹ Au_{130} ,¹² and Au_{246} ¹⁴ display decahedral cores; and Au_{133} ¹³ has a Mackay icosahedral core. Au_{146} is the largest solved cluster with a FCC core. In addition, it is the smallest gold nanoparticle observed

containing a stacking fault. These planar defects are very common in much larger particles (such as colloidal gold) but have never been observed at this low number of atoms.

Although icosahedral and decahedral structures display energetically favorable close-packed outer facets, as the size of the particle increases, a preference for bulk-like FCC structures is expected. Whereas nucleation mechanisms remain unclear, most likely FCC nanoparticles should grow starting from FCC seeds. The favorability of a cluster as a seed for an FCC particle is linked to the ability to grow quickly and leave the subcritical size region before disintegration.²⁸ The twinned-FCC anti-cuboctahedral kernel of Au₁₄₆ may therefore be a more suitable seed than a cuboctahedral kernel, as the saturation of {100} facets in J27 generates extra sites with four-coordination on the twin plane that are absent in the untwinned structure (Figure S10). This creation of four-coordination sites is similar to the well-established effect of twins in the growth of nanoparticles.²⁹ In the case of nanoparticles, the introduction of twins favors a kinetic growth on the twin that leads to thermodynamically unfavorable shapes like triangular plates or rods in a similar fashion that screw dislocations favor the growth of large crystals.³⁰

We have shown that even an FCC structure with such few atoms (Au₁₄₆, ~1.7 nm) contains a well-defined twinning plane. Considering that decahedral structures have five twin-planes and icosahedra have 30 twin-planes, twinning appears to be a critical component of nanoparticle structure from a very early stage of growth. Moreover, to our knowledge, the subatomic resolution structure of Au₁₄₆(p-MBA)₅₇ presented here is the first such structure of a metal cluster obtained by electron diffraction of frozen hydrated samples, establishing MicroED as a new and important tool for the characterization of nanomaterials.

EXPERIMENTAL METHODS

Synthesis and Purification of Gold Nanoclusters. The gold nanoclusters were produced by the two-phase method with some minor modifications.^{23,31–33} First, stock solution of *para*-mercaptobenzoic acid (p-MBA) at 100 mM was prepared in 300 mM NaOH by vigorous stirring for at least 3 h or overnight and pulsed sonication. Nanoclusters were typically produced in 25 mL batches in 50% v/v methanol in a 50 mL round flask by adding aqueous HAuCl₄ to a final concentration of 3 mM and p-MBA to 9 mM. The color of this solution was light yellow. The mixture was stirred overnight until solution was almost clear/colorless. Then, freshly prepared ice-cold aqueous NaBH₄ was added to achieve 1.5 mM final concentration, and the reaction proceeded for 2 h. The entire content was transferred to a 50 mL conical tube. Volume was completed to 50 mL with cold methanol. Two distinct approaches were used to precipitate the as-prepared cluster product: cold methanol or cold methanol with 100 mM ammonium acetate. The content was mixed gently and incubated at 4 °C. Nanoclusters were concentrated with centrifugation at 2000–3000 rpm for 15 min, supernatant was removed, and the pellet was resuspended in 25 mL of methanol. Nanoclusters were again concentrated by centrifugation at 2000–3000 rpm for 15 min, supernatant was removed, and the pellet was air-dried. Finally, the pellet was dissolved in a small volume with ultrapure ddH₂O (0.5 to 1 mL). Product quality was assessed by native 10–12% PAGE in TBE buffer at 100 V. Major bands corresponding to gold nanoclusters were cut from the gel to separate the fractions of interest and then reconcentrated by precipitation with

methanol or rotary evaporator. Aliquots in ultrapure ddH₂O were stored at 4 °C for further analysis. Stability of gold nanoclusters in both samples, with and without ammonium acetate coprecipitation, was monitored by routine 10–12% PAGE, UV–vis, and transmission electron microscopy (TEM), confirming no perceivable changes over 6 months.

Gold Cluster Crystallization. The two cluster samples, with and without ammonium acetate coprecipitation, were submitted to crystallization screenings. The sample without ammonium acetate formed poorly diffracting hexagonal plates, whereas the sample coprecipitated with ammonium acetate crystallized in the presence of 25% polyethylene glycol 8000 (PEG8K) and 50 mM sodium potassium phosphate. Crystals were transferred to a stabilizing solution for cryo-protection containing 25% methyl pentanediol (MPD), 5% PEG 8K, and 50 mM sodium potassium phosphate.

Electron Micro-Diffraction (MicroED). Crystals were too big for MicroED, and thus a fragmentation protocol was designed.³⁴ Crystals in stabilizing solution (see above) were harvested in a 0.5 mL Eppendorf tube, and 30 mg of stainless-steel beads (1 mm diameter) was placed for fragmentation.^{35,36} Sample was vortexed several times, and the presence of homogeneously sized fragments was verified using bright-field microscopy. Stainless-steel beads were removed using a magnet, and samples were centrifuged at 1000 rpm to pellet the fragments. Excess of mother liquor was removed to obtain a concentrated slurry, and stabilizing cryo-protecting solution was added and mixed carefully with the slurry. This procedure was repeated three times to ensure full buffer exchange. Holey 300 mesh carbon Quantifoil R2/2 grids were negatively glow discharged at 25 mA and 2×10^{-1} mbar for 30 s from both sides. Then, 2 μ L of the concentrated and cryoprotected nanocrystal solution was pipetted onto the grid and incubated for 1 min before the excess liquid was removed by careful blotting from the backside using Fisherbrand P2 filter paper. Afterward the grid was flash-frozen by plunging it into liquid nitrogen. The grids were stored in liquid nitrogen until they were used for data collection.

MicroED Data were collected using an FEI Titan Krios TEM equipped with a field-emission gun operating at 300 kV, corresponding to an electron wavelength of 0.0197 Å.^{25,26} Data were recorded with a TVIPS TemCam-F416 4K \times 4K CMOS camera with sensor pixel dimensions of 15.6 μ m \times 15.6 μ m. Images were taken in rolling-shutter mode with 2 \times -pixel binning, resulting in final images of 2048 px \times 2048 px. Frames were acquired under a continuous rotation of 0.1°/s every 5 s or a 0.5° wedge of reciprocal space per frame. Data was converted using open-source software and corrected for pixel truncation, as previously described.^{37,38} MicroED experiments were performed at liquid nitrogen temperatures, ~77 K. Nanocrystals diffracted to 0.7 Å resolution by MicroED.

Structure Refinement. X-ray and MicroED data were processed in space group *P1* using the software package XDS.³⁹ Reflections were indexed using the program XPREP in *P2(1)/n* or *P2(1)/c*. The X-ray structure was solved using the program SHELXT⁴⁰ yielding 146 gold and 57 sulfur atoms. The $F_o - F_c$ difference map using X-ray data set 2 (Table S1) showed positive density for 40 pMBA molecules. The full model was completed using the difference map ($F_o - F_c$) from X-ray data set 1 (Table S1), which revealed all 57 pMBA molecules (Figure S3c,d). The MicroED structure was solved using a partial solution obtained with the program Shake and Bake,⁴¹ where 79 Au atoms were clearly identified in the

Patterson map. The remaining Au atoms and all 57 sulfurs were easily identified as positive density in the $F_o - F_c$ map. Only a few p-MBA molecules were observed in the MicroED data.

The MicroED and X-ray structures were refined using the programs SHELXL⁴² and Phenix.⁴³ Several rounds of manual building and refinement were employed to place the pMBA molecules.

Mass Spectrometry. Samples were analyzed by HPLC-ESI-ToF-MS. The LC-MS method resolves (separates) multi-component samples (chromatographically) prior to the identification of each component (mass-spectrometrically), reducing interference from adducts.^{44,45} Au₁₀₂(pMBA)₄₄ clusters were used for validation of the quality of the technique. The Au₁₄₆ clusters were detected intact. The major peak could be cleanly attributed to the intact (146,57) species, in the charge-states = [4-] thru [7-], with [5-] dominant. Minor satellite peaks could be attributed to water adduction.

Computational DFT Methods. The ab initio DFT structural optimization started from the experimental structure. Subsequently, the structure was relaxed using the VASP code^{46,47} with PAWs until all forces were <0.02 eV/Å. An energy cutoff of 280 eV was employed. A charge state of 3- (three additional electrons) was used to comply with the expected electronic shell closing at 2008 electrons according to the superatom model. Among our various optimizations with distinct exchange-correlation functionals, ligand models (SR: Cl⁻, R: CH₃, or SR: pMBA), and charge states {3+, 1+, 1-, 3-}, the LDA optimization chg. = 3- turns out to best represent the Au-Au bonds, unlike the calculations done using a GGA functional (PBE; not shown), to which the missing hydrogen atoms were added.

■ ASSOCIATED CONTENT

■ Supporting Information

The Supporting Information is available free of charge on the ACS Publications website at DOI: 10.1021/acs.jpcl.7b02621.

Crystallographic data summary, mass spectroscopy, and DFT results. (PDF)

X-ray Data Set 1 (SLS: XO6SA-PXI). (CIF)

X-ray Data Set 2 (APS: SERCAT-22ID). (CIF)

MicroED Data Set (Janelia: Titan Krios). (CIF)

Movie S1. 360° rotation of the structure of Au₁₄₆(pMBA)₅₇ cluster. (MPG)

■ AUTHOR INFORMATION

Corresponding Authors

*G.C.: E-mail: guc9@pitt.edu.

*T.G.: E-mail: tgonen@ucla.edu.

*R.L.W.: E-mail: robert.whetten@utsa.edu.

*M.J.Y.: E-mail: Miguel.yacaman@utsa.edu.

ORCID

David M. Black: 0000-0003-2757-447X

Guillermo Calero: 0000-0003-3730-4676

Present Addresses

#C.O.B.: Division of Biology and Biological Engineering, California Institute of Technology, Pasadena, CA, USA.

▽M.J.d.I.C.: Structural Biology Program, Sloan Kettering Institute, Memorial Sloan Kettering Cancer Center, New York, NY, USA.

Author Contributions

○S.V., D.A.L., and M.W.M. contributed equally to this work.

Notes

The authors declare no competing financial interest.

■ ACKNOWLEDGMENTS

We acknowledge May Elizabeth Sharp and Meitan Wang at the Swiss Light Source (SLS), Michael Becker and Craig Ogata at GM/CA (Argonne National Laboratory), and John Chrzas and Rod Salazar at the South East Regional Collaborative Access Team (SERCAT, Argonne National Laboratory). We acknowledge Aina Cohen and Jinhu Song from the Macromolecular Femtosecond Crystallography (MFX) at the Linac Coherent Light Source (LCLS) for their support during data collection. We thank D. Lee for home-source X-ray technical support at the University of Pittsburgh. Research reported in this publication was supported by the National Institute on Minority Health and Health Disparities (NIMHD) of the National Institutes of Health (#G12-MD007591) and by The Welch Foundation grants #AX-1615 and #AX-1857. G.C. acknowledges University of Pittsburgh startup funds and support from NIH grants P50-GM082251, R01-GM112686, and BioXFEL-STC1231306. GM/CA@aps has been funded in whole or in part with Federal funds from the National Cancer Institute (ACB-12002) and the National Institute of General Medical Sciences (AGM-12006). Use of the Advanced Photon Source was supported by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences, under Contract No. W-31-109-Eng-38. Use of the Linac Coherent Light Source (LCLS), SLAC National Accelerator Laboratory, is supported by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences under Contract No. DE-AC02-76SF00515. The Gonen laboratory is supported by the Howard Hughes Medical Institute, and this work was also supported by the Janelia Research Campus visitor program. The contents of this publication are solely the responsibility of the authors and do not necessarily represent the official views of NIGMS or NIH.

■ REFERENCES

- (1) Negishi, Y.; Nakazaki, T.; Malola, S.; Takano, S.; Niihori, Y.; Kurashige, W.; Yamazoe, S.; Tsukuda, T.; Hakkinen, H. A Critical Size for Emergence of Nonbulk Electronic and Geometric Structures in Dodecanethiolate-Protected Au Clusters. *J. Am. Chem. Soc.* **2015**, *137*, 1206–1212.
- (2) Zhou, M.; Zeng, C. J.; Chen, Y. X.; Zhao, S.; Sfeir, M. Y.; Zhu, M. Z.; Jin, R. C. Evolution from the Plasmon to Exciton State in Ligand-Protected Atomically Precise Gold Nanoparticles. *Nat. Commun.* **2016**, *7*, 13240.
- (3) Zeng, C.; Chen, Y.; Iida, K.; Nobusada, K.; Kirschbaum, K.; Lambright, K. J.; Jin, R. Gold Quantum Boxes: On the Periodicities and the Quantum Confinement in the Au(2)(8), Au(3)(6), Au(4)(4), and Au(5)(2) Magic Series. *J. Am. Chem. Soc.* **2016**, *138*, 3950–3953.
- (4) Zeng, C.; Li, T.; Das, A.; Rosi, N. L.; Jin, R. Chiral Structure of Thiolate-Protected 28-Gold-Atom Nanocluster Determined by X-Ray Crystallography. *J. Am. Chem. Soc.* **2013**, *135*, 10011–10013.
- (5) Zeng, C.; Qian, H.; Li, T.; Li, G.; Rosi, N. L.; Yoon, B.; Barnett, R. N.; Whetten, R. L.; Landman, U.; Jin, R. Total Structure and Electronic Properties of the Gold Nanocrystal Au₃₆(SR)₂₄. *Angew. Chem., Int. Ed.* **2012**, *51*, 13114–13118.
- (6) Crasto, D.; Malola, S.; Brofsky, G.; Dass, A.; Hakkinen, H. Single Crystal Xrd Structure and Theoretical Analysis of the Chiral Au_{30S}(S-T-Bu)₁₈ Cluster. *J. Am. Chem. Soc.* **2014**, *136*, 5000–5005.
- (7) Qian, H.; Eckenhoff, W. T.; Zhu, Y.; Pintauer, T.; Jin, R. Total Structure Determination of Thiolate-Protected Au₃₈ Nanoparticles. *J. Am. Chem. Soc.* **2010**, *132*, 8280–8281.

- (8) Yang, S.; Chai, J.; Song, Y.; Kang, X.; Sheng, H.; Chong, H.; Zhu, M. A New Crystal Structure of Au₃₆ with a Au₁₄ Kernel Capped by Thiolate and Chloride. *J. Am. Chem. Soc.* **2015**, *137*, 10033–10035.
- (9) Heaven, M. W.; Dass, A.; White, P. S.; Holt, K. M.; Murray, R. W. Crystal Structure of the Gold Nanoparticle [N(C₈H₁₇)₄][Au₂₅(SCH₂CH₂Ph)₁₈]. *J. Am. Chem. Soc.* **2008**, *130*, 3754–3755.
- (10) Zeng, C.; Liu, C.; Chen, Y.; Rosi, N. L.; Jin, R. Atomic Structure of Self-Assembled Monolayer of Thiolates on a Tetragonal Au₉₂ Nanocrystal. *J. Am. Chem. Soc.* **2016**, *138*, 8710–8713.
- (11) Jadzinsky, P. D.; Calero, G.; Ackerson, C. J.; Bushnell, D. A.; Kornberg, R. D. Structure of a Thiol Monolayer-Protected Gold Nanoparticle at 1.1 Å Resolution. *Science* **2007**, *318*, 430–433.
- (12) Chen, Y.; Zeng, C.; Liu, C.; Kirschbaum, K.; Gayathri, C.; Gil, R. R.; Rosi, N. L.; Jin, R. Crystal Structure of Barrel-Shaped Chiral Au₁₃₀(p-MBT)₅₀ Nanocluster. *J. Am. Chem. Soc.* **2015**, *137*, 10076–10079.
- (13) Zeng, C.; Chen, Y.; Kirschbaum, K.; Appavoo, K.; Sfeir, M. Y.; Jin, R. Structural Patterns at All Scales in a Nonmetallic Chiral Au(133)(SR)₅₂ Nanoparticle. *Sci. Adv.* **2015**, *1*, e1500045.
- (14) Zeng, C.; Chen, Y.; Kirschbaum, K.; Lambright, K. J.; Jin, R. Emergence of Hierarchical Structural Complexities in Nanoparticles and Their Assembly. *Science* **2016**, *354*, 1580–1584.
- (15) Philip, R.; Chantharasupawong, P.; Qian, H. F.; Jin, R. C.; Thomas, J. Evolution of Nonlinear Optical Properties: From Gold Atomic Clusters to Plasmonic Nanocrystals. *Nano Lett.* **2012**, *12*, 4661–4667.
- (16) Yi, C.; Zheng, H.; Tvedte, L. M.; Ackerson, C. J.; Knappenberger, K. L. Nanometals: Identifying the Onset of Metallic Relaxation Dynamics in Monolayer-Protected Gold Clusters Using Femtosecond Spectroscopy. *J. Phys. Chem. C* **2015**, *119*, 6307–6313.
- (17) Cleveland, C. L.; Landman, U.; Schaaff, T. G.; Shafiqullin, M. N.; Stephens, P. W.; Whetten, R. L. Structural Evolution of Smaller Gold Nanocrystals: The Truncated Decahedral Motif. *Phys. Rev. Lett.* **1997**, *79*, 1873–1876.
- (18) Whetten, R. L.; Khoury, J. T.; Alvarez, M. M.; Murthy, S.; Vezmar, I.; Wang, Z.; Stephens, P. W.; Cleveland, C. L.; Luedtke, W.; Landman, U. Nanocrystal Gold Molecules. *Adv. Mater.* **1996**, *8*, 428–433.
- (19) Lopez-Acevedo, O.; Akola, J.; Whetten, R. L.; Grönbeck, H.; Häkkinen, H. Structure and Bonding in the Ubiquitous Icosahedral Metallic Gold Cluster Au₁₄₄(SR)₆₀. *J. Phys. Chem. C* **2009**, *113*, 5035–5038.
- (20) Bahena, D.; Bhattarai, N.; Santiago, U.; Tlahuice, A.; Ponce, A.; Bach, S. B. H.; Yoon, B.; Whetten, R. L.; Landman, U.; Jose-Yacaman, M. STEM Electron Diffraction and High-Resolution Images Used in the Determination of the Crystal Structure of the Au₁₄₄(SR)₆₀ Cluster. *J. Phys. Chem. Lett.* **2013**, *4*, 975–981.
- (21) Jensen, K. M.; Juhas, P.; Tofanelli, M. A.; Heinecke, C. L.; Vaughan, G.; Ackerson, C. J.; Billinge, S. J. Polymorphism in Magic-Sized Au₁₄₄(SR)₆₀ Clusters. *Nat. Commun.* **2016**, *7*, 11859.
- (22) Plascencia-Villa, G.; Demeler, B.; Whetten, R. L.; Griffith, W. P.; Alvarez, M.; Black, D. M.; Jose-Yacaman, M. Analytical Characterization of Size-Dependent Properties of Larger Aqueous Gold Nanoclusters. *J. Phys. Chem. C* **2016**, *120*, 8950–8958.
- (23) Mustalahti, S.; Myllyperkiö, P.; Lahtinen, T.; Salorinne, K.; Malola, S.; Koivisto, J.; Häkkinen, H.; Pettersson, M. Ultrafast Electronic Relaxation and Vibrational Cooling Dynamics of Au₁₄₄(SC₂H₄Ph)₆₀ Nanocluster Probed by Transient Mid-IR Spectroscopy. *J. Phys. Chem. C* **2014**, *118*, 18233–18239.
- (24) Wong, O. A.; Heinecke, C. L.; Simone, A. R.; Whetten, R. L.; Ackerson, C. J. Ligand Symmetry-Equivalence on Thiolate Protected Gold Nanoclusters Determined by NMR Spectroscopy. *Nanoscale* **2012**, *4*, 4099–4102.
- (25) Shi, D.; Nannenga, B. L.; Iadanza, M. G.; Gonen, T. Three-Dimensional Electron Crystallography of Protein Microcrystals. *eLife* **2013**, *2*, e01345.
- (26) Nannenga, B. L.; Shi, D.; Leslie, A. G.; Gonen, T. High-Resolution Structure Determination by Continuous-Rotation Data Collection in MicroED. *Nat. Methods* **2014**, *11*, 927–930.
- (27) Doye, J. P. K.; Wales, D. J. Structural Consequences of the Range of the Interatomic Potential - A Menagerie of Clusters. *J. Chem. Soc., Faraday Trans.* **1997**, *93*, 4233–4243.
- (28) van de waal, B. W. An Atomic-Scale Model of Fcc Crystal-Growth. *Z. Phys. D: At., Mol. Clusters* **1991**, *20*, 349–352.
- (29) Lofton, C.; Sigmund, W. Mechanisms Controlling Crystal Habits of Gold and Silver Colloids. *Adv. Funct. Mater.* **2005**, *15*, 1197–1208.
- (30) Burton, W. K.; Cabrera, N.; Frank, F. C. The Growth of Crystals and the Equilibrium Structure of Their Surfaces. *Philos. Trans. R. Soc., A* **1951**, *243*, 299.
- (31) Alvarez, M. M.; Chen, J.; Plascencia-Villa, G.; Black, D. M.; Griffith, W. P.; Garzon, I. L.; Jose-Yacaman, M.; Demeler, B.; Whetten, R. L. Hidden Components in Aqueous "Gold-144" Fractionated by PAGE: High-Resolution Orbitrap ESI-MS Identifies the Gold-102 and Higher All-Aromatic Au-pMBA Cluster Compounds. *J. Phys. Chem. B* **2016**, *120*, 6430–6438.
- (32) Tvedte, L. M.; Ackerson, C. J. Size-Focusing Synthesis of Gold Nanoclusters with p-Mercaptobenzoic Acid. *J. Phys. Chem. A* **2014**, *118*, 8124–8128.
- (33) Heinecke, C. L.; Ackerson, C. J. Preparation of Gold Nanocluster Bioconjugates for Electron Microscopy. In *Nanoimaging: Methods and Protocols*, Sousa, A. A., Kruhlak, M. J., Eds.; Humana Press: Totowa, NJ, 2013; pp 293–311.
- (34) de la Cruz, M. J.; Hattne, J.; Shi, D.; Seidler, P.; Rodriguez, J.; Reyes, F. E.; Sawaya, M. R.; Cascio, D.; Weiss, S. C.; Kim, S. K.; Hinck, C. S.; Hinck, A. P.; Calero, G.; Eisenberg, D.; Gonen, T. Atomic-Resolution Structures from Fragmented Protein Crystals with the CryoEM Method MicroED. *Nat. Methods* **2017**, *14*, 399–402.
- (35) Stevenson, H. P.; Lin, G.; Barnes, C. O.; Sutkeviciute, I.; Krzysiak, T.; Weiss, S. C.; Reynolds, S.; Wu, Y.; Nagarajan, V.; Makhov, A. M.; Lawrence, R.; Lamm, E.; Clark, L.; Gardella, T. J.; Hogue, B. G.; Ogata, C. M.; Ahn, J.; Gronenborn, A. M.; Conway, J. F.; Vilardaga, J. P.; Cohen, A. E.; Calero, G. Transmission Electron Microscopy for the Evaluation and Optimization of Crystal Growth. *Acta Crystallogr. D Struct. Biol.* **2016**, *72*, 603–615.
- (36) Barnes, C. O.; Kovaleva, E. G.; Fu, X.; Stevenson, H. P.; Brewster, A. S.; DePonte, D. P.; Baxter, E. L.; Cohen, A. E.; Calero, G. Assessment of Microcrystal Quality by Transmission Electron Microscopy for Efficient Serial Femtosecond Crystallography. *Arch. Biochem. Biophys.* **2016**, *602*, 61–68.
- (37) Hattne, J.; Shi, D.; de la Cruz, M. J.; Reyes, F. E.; Gonen, T. Modeling Truncated Pixel Values of Faint Reflections in MicroED Images. *J. Appl. Crystallogr.* **2016**, *49*, 1029–1034.
- (38) Hattne, J.; Reyes, F. E.; Nannenga, B. L.; Shi, D.; de la Cruz, M. J.; Leslie, A. G.; Gonen, T. MicroED Data Collection and Processing. *Acta Crystallogr., Sect. A: Found. Adv.* **2015**, *71*, 353–360.
- (39) Kabsch, W. XDS. *Acta Crystallogr., Sect. D: Biol. Crystallogr.* **2010**, *66*, 125–132.
- (40) Sheldrick, G. M. Shelx - Integrated Space-Group and Crystal-Structure Determination. *Acta Crystallogr., Sect. A: Found. Adv.* **2015**, *71*, 3–8.
- (41) Miller, R.; Gallo, S. M.; Khalak, H. G.; Weeks, C. M. Sbn - Crystal-Structure Determination Via Shake-and-Bake. *J. Appl. Crystallogr.* **1994**, *27*, 613–621.
- (42) Sheldrick, G. M. A Short History of Shelx. *Acta Crystallogr., Sect. A: Found. Crystallogr.* **2008**, *64*, 112–122.
- (43) Adams, P. D.; Afonine, P. V.; Bunkoczi, G.; Chen, V. B.; Davis, I. W.; Echols, N.; Headd, J. J.; Hung, L. W.; Kapral, G. J.; Grosse-Kunstleve, R. W.; McCoy, A. J.; Moriarty, N. W.; Oeffner, R.; Read, R. J.; Richardson, D. C.; Richardson, J. S.; Terwilliger, T. C.; Zwart, P. H. Phenix: A Comprehensive Python-Based System for Macromolecular Structure Solution. *Acta Crystallogr., Sect. D: Biol. Crystallogr.* **2010**, *66*, 213–221.
- (44) Black, D. M.; Bach, S. B.; Whetten, R. L. Capillary Liquid Chromatography Mass Spectrometry Analysis of Intact Monolayer-Protected Gold Clusters in Complex Mixtures. *Anal. Chem.* **2016**, *88*, 5631–5636.

(45) Black, D. M.; Alvarez, M. M.; Yan, F.; Griffith, W. P.; Plascencia-Villa, G.; Bach, S. B. H.; Whetten, R. L. Triethylamine Solution for the Intractability of Aqueous Gold–Thiolate Cluster Anions: How Ion Pairing Enhances ESI-MS and HPLC of aq-Aun(pMBA)_n. *J. Phys. Chem. C* **2017**, *121*, 10851–10857.

(46) Kresse, G.; Furthmüller, J. Efficiency of Ab-Initio Total Energy Calculations for Metals and Semiconductors Using a Plane-Wave Basis Set. *Comput. Mater. Sci.* **1996**, *6*, 15–50.

(47) Kresse, G.; Joubert, D. From Ultrasoft Pseudopotentials to the Projector Augmented-Wave Method. *Phys. Rev. B: Condens. Matter Mater. Phys.* **1999**, *59*, 1758–1775.